

An Evaluation of Intra-orifice Sealing Materials for Coronal Microleakage in Obturated Root Canals

Qian Zhou JIANG¹, Qi ZHANG², Jie HE^{2,3}

Objective: To compare three flowable composites (*Esthet-X flow*, *Beautiful flow* and *Filtek Z350*) with a hybrid composite (*Z100*), and two temporary filling materials (*Cavit* and *IRM*) as intra-orifice filling materials to prevent coronal microleakage.

Methods: Root canal treatments were performed on 104 extracted human single-rooted premolars. Three millimetres of coronal gutta-percha was replaced by one of the six filling materials to seal the intra-orifice. After thermocycling (5°C to 55°C) for 750 cycles and immersion in Indian dye for 5 days, the teeth were evaluated for dye penetration along canal walls. The data were analysed with the Kruskal–Wallis test and the Mann–Whitney U test.

Results: All of the three flowable composites sealed the intra-orifice of root canals as well as *Z100*, but significantly better than *Cavit* and *IRM*. There was no significant difference among the three flowable composites, or between *Cavit* and *IRM*.

Conclusion: Flowable composites are ideal intra-orifice seals.

Key words: coronal leakage, flowable composite, intra-orifice seal

Endodontic therapy aims to eliminate infection in the root canal system and to prevent re-infection from apical and coronal directions. While both apical and coronal leakages are major causes leading to root canal treatment failure, coronal leakage is thought to be a more important factor deciding the clinical outcome¹. Thus, the prevention of coronal leakage has been the top clinical priority.

To prevent coronal leakage, Roghanizad and Jones first placed a coronal seal into the orifice of the root canals to replace part of the gutta-percha immediately after root canal filling². They replaced 3 mm of gutta-percha with *Cavit*TM (3M, ESPE, Germany) resin-based temporary restorative material (*TERM*, Dentsply International, USA) or amalgam with cavity varnish, and found that amalgam with two coats of cavity varnish sealed significantly better than *Cavit* and *TERM*. However, amalgam causes tooth discoloration and interferes with future bonding agents. Since then, a variety of materials have been tested for intra-orifice seals, including zinc oxide preparations, glass ionomer cements and composite resins.

A couple of zinc oxide preparations were previously compared³⁻⁵, but the results were not conclusive. For example, *Cavit* was shown to have better sealing ability than immediate restorative material (*IRM*) and *Super-EBA*, but wore off faster than the latter³. In addition, the free eugenol in *IRM* and *Super-EBA* was found to interfere with dentinal bonding agents and polymerisation of composite resins. In another study, Balto et al found no significant difference in coronal leakage between *Cavit*,


1 Department of Endodontics, School and Hospital of Stomatology, Wuhan University, Wuhan, P.R. China.

2 Key Laboratory of Oral Biomedical Engineering of Ministry of Education, School and Hospital of Stomatology, Wuhan University, Wuhan, P.R. China.

3 Department of Endodontics, Wuhan General Hospital of Guangzhou Command, Wuhan, P.R. China.

Corresponding author: Dr Qi ZHANG, Key Laboratory of Oral Biomedical Engineering of Ministry of Education, School and Hospital of Stomatology, Wuhan University, Luoyu Road 237, Wuhan 430079, P.R. China. Tel: 86-27-87686268; Fax: 86-27-87647443; Email: zhangqimary@yahoo.com.cn

This work was supported by the National Natural Science Foundation of China (grant No. 30400499), Hubei Natural Science Foundation (grant No. 2004ABB017) and Hubei Innovative Research Team (grant No. 2004ABC004).

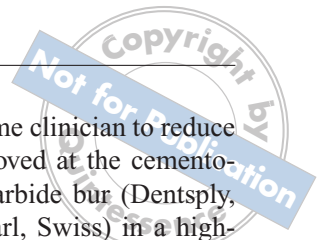

IRM and TempBond® (Kerr Corporation, Japan) (10 parts zinc oxide and 1 part eugenol) after post space preparation⁴. However, a recent study found that two new temporary materials, Tempit Ultra-F (Centrix, Japan) and Tempit (Centrix, Japan), had less leakage than Cavit and IRM⁵.

Different glass ionomer cements were also compared. Wolcott et al tested three pigmented glass ionomer cements⁶. Of those, Vitrebond™ (3M, ESPE) was found to be better than Ketac-Bond™ (3M, ESPE) or GC America (Chicago, IL, USA) and was suggested to be an ideal intra-orifice barrier. While glass ionomer cements are good intra-orifice barriers, other materials may perform better. For example, composite resins (denture sealants and TERM) sealed more effectively than glass ionomer cements in preventing coronal leakage⁷. In recent years, composite resins have become more popular.

Among them, flowable composites have stood out as ideal intra-orifice sealing materials due to their superior advantages. They have high flowability, ability to form layers of minimum thickness, high flexibility, radiopaqueness and are available in different colours⁸. During the preparation of the present study, two other *in vitro* studies examined microleakage of flowable composites as intra-orifice sealing materials, but found inconsistent and inconclusive results^{9,10}. Jenkins et al found the flowable composite Teric sealed better than Cavit and ProRoot™ MTA (Dentsply International)⁹, whereas Sauer et al found the flowable composite Flow-it exhibited more leakage than Cavit and Vitremer (3M, ESPE) (a glass ionomer cement)¹⁰. Therefore, it is necessary to further study the sealing ability of flowable composites as intra-orifice barriers.

The present study aimed to evaluate and compare three flowable composites (Esthet-X flow [Dentsply, USA], Beautifil flow [Shofu, Kyoto, Japan] and Filtek Z350 [3M, ESPE]), a hybrid composite (Z100), and two temporary materials (Cavit and IRM) as intra-orifice filling materials for the prevention of coronal leakage in the absence of coronal restoration.

Materials and Methods

A total of 104 single-rooted premolars extracted for orthodontic reasons were used in the present study. All teeth were examined clinically under a surgical operating microscope. Teeth with cracks, root resorption, open foramen, and calcified and curved canals were excluded. The external surfaces of the roots were cleaned with curettes to remove any debris and/or calculus, with attention not to damage the root surface.

All teeth were treated by the same clinician to reduce variability. The crowns were removed at the cemento-enamel junction (CEJ) using a carbide bur (Dentsply, Maillefer Instruments Holding Sarl, Swiss) in a high-speed handpiece with an air/water spray. The instrumentation technique used for cleaning and shaping was performed as follows: working length was established by placing a #10 K file (Dentsply Maillefer, Ballaigues, Switzerland) into the canal until visible at the apical foramen and subtracting 1 mm. A ProTaper® (Dentsply Maillefer, Ballaigues, Switzerland) Sx file was used to flare the orifice. ProTaper S1, S2, F1, F2 and F3 files were used sequentially according to the manufacturer's instructions in a crown-down technique. A total of 5 ml of 5.25% sodium hypochlorite (NaOCl) was used to irrigate the canals between each file. Once the final apical size was reached, the smear layer was removed by using 5 ml of 17% ethylenediaminetetraacetic acid (EDTA) followed by 5 ml of 5.25% NaOCl and 5 ml of distilled water¹⁰. All canals were dried with paper points (Gapadent, Tianjin, P.R. China).

All roots were obturated with 0.06 greater taper gutta-percha (Meta Biomed, Cheongju, Korea) and AH Plus sealer (Dentsply DeTrey, Konstanz, Germany) by using the continuous wave of condensation technique (E&Q system, Meta Biomed)⁵. The plugger (Dentsply Maillefer) was used compact the gutta-percha. The gutta-percha was seared off 3 mm apical to the orifice, leaving the space for experimental materials. Excess root canal sealer was removed with alcohol-wet cotton pellets. The root filling technique was conducted while the teeth were maintained in moist saline-soaked gauze. Complete obturation of all canals was confirmed with radiographs taken in buccal-lingual and mesial-distal directions. All teeth were placed in 100% humidity at 37°C for 48 hours to allow the root canal sealer to set.

The teeth were randomly divided into six experimental groups of 14 teeth using different orifice sealing materials as follows: group 1, Esthet-X flow; group 2, Beautifil flow F02; group 3, Filtek Z350 flowable restorative; group 4, Z100 restorative; group 5, Cavit G; group 6, IRM (Table 1). The remaining 20 teeth were divided equally to positive (root-treated canals without intra-orifice sealing) and negative control (intact teeth) groups.

The coronal root canal spaces were dried, and the restorative materials were placed following the manufacturers' instructions.

The materials were inserted and adapted in the prepared 3-mm deep cavity over the root canal filling; excess material was removed. In brief, the specimens of groups 1, 2, 3 and 4 were etched with 37% phosphoric acid (H₃PO₄), washed and then gently dried with air spray.

Table 1 Materials used in the study

| Materials | Manufacturer | Type | Shade | Bonding system |
|-----------------------------------|---------------------------------|---|-------|-------------------------------------|
| Esthet-X® flow | Dentsply/Caulk Milford, DE, USA | Liquid micro hybrid | A3 | Prime & Bond® NT™ (full-acid) |
| Beautifil® flow F02 (low flow) | Shofu, Kyoto, Japan | Fluoride releasing flowable restorative | – | FL-Bond II (self-acid) |
| Filtek™ Z350 flowable restorative | 3M ESPE, St Paul, MN, USA | Nano-filled restorative | A2 | Adper™ Single Bond Plus (self-acid) |
| Z100™ restorative | 3M ESPE, St Paul, MN, USA | Hybrid resin composite | A3 | Adper™ Single Bond Plus (self-acid) |
| Cavit™ G | 3M ESPE, Seefeld, Germany | Temporary filling material | – | – |
| IRM® | Dentsply/Caulk Milford, DE, USA | Intermediate restorative | – | – |

Table 2 Mean dye penetration measurements (mm)

| Material | Number of teeth | Mean dye penetration | SD | Range |
|-----------------|-----------------|----------------------|------|---------|
| Esthet-X® flow | 14 | 0.58 | 0.45 | 0–1.1 |
| Beautifil® flow | 13 | 0.66 | 0.51 | 0–1.5 |
| Filtek™ Z350 | 14 | 0.81 | 0.68 | 0–2.2 |
| Z100™ | 14 | 0.93 | 1.39 | 0–4.1 |
| Cavit™ G | 14 | 1.52 | 0.95 | 0.6–4.3 |
| IRM® | 13 | 2.01 | 1.39 | 0.7–4.4 |
| Positive | 10 | 3.66 | 1.32 | 1.7–5.4 |
| Negative | 10 | 0.00 | 0.00 | 0 |

Bonding systems (Table 1) were applied to the dentine using a saturated disposable brush. The excess was removed by a quick air spray and then cured with a visible light activator (Dentsply DeTrey). The composites were injected or inserted into the cavity in two layers and each layer was cured with a visible light activator for 40 s. In groups 5 and 6, Cavit G or IRM was placed into the prepared root canal cavity over the gutta-percha and then condensed individually with the plugger. The excess was removed with a moistened sterilised cotton pellet.

All of the experimental teeth and positive control group received three layers of nail polish, leaving only the area of the canal's orifice exposed to provide uniform control of any lateral or accessory canals. All surfaces of the negative control group were completely sealed with three layers of nail polish.

The specimens were subjected to thermocycling between 5°C and 55°C for 750 cycles. The dwell times in each bath and the time intervals at room temperature between baths were 1 minute¹⁰. Subsequently, the teeth were immersed in Indian ink for 5 days. Following exposure to the dye, the teeth were rinsed in tap water and

the nail polish was completely removed with a scalpel. Then the teeth were decalcified in 5% hydrochloric acid (HCl) for 3 days with constant stirring followed by a running water wash. The teeth were dehydrated for 3 hours in each of 50%, 75% and 95% ethyl alcohol and 2 hours in 100% ethyl alcohol, and then cleared by immersion into methyl salicylate. Two specimens were lost during rinsing procedures, thus group 4 (Beautifil flow) and group 6 (IRM) had 13 specimens each.

The experimental materials were observed over 360 degrees and leakage was observed by a calibrated examiner using a ×10 stereomicroscope (Carl Zeiss Vision, München-Hallbergmoos, Germany). The leakage was measured to the greatest penetration from the coronal extent of the orifice material to the nearest 0.1 mm.

Kruskal–Wallis analysis was performed to identify whether or not there was at least one statistically significant difference among the groups, and a Mann–Whitney *U* test was performed to determine which group was different from the others with the SPSS statistical program version 10.0 (SPSS, Chicago, IL, USA). The level of significance was set at $P < 0.05$.

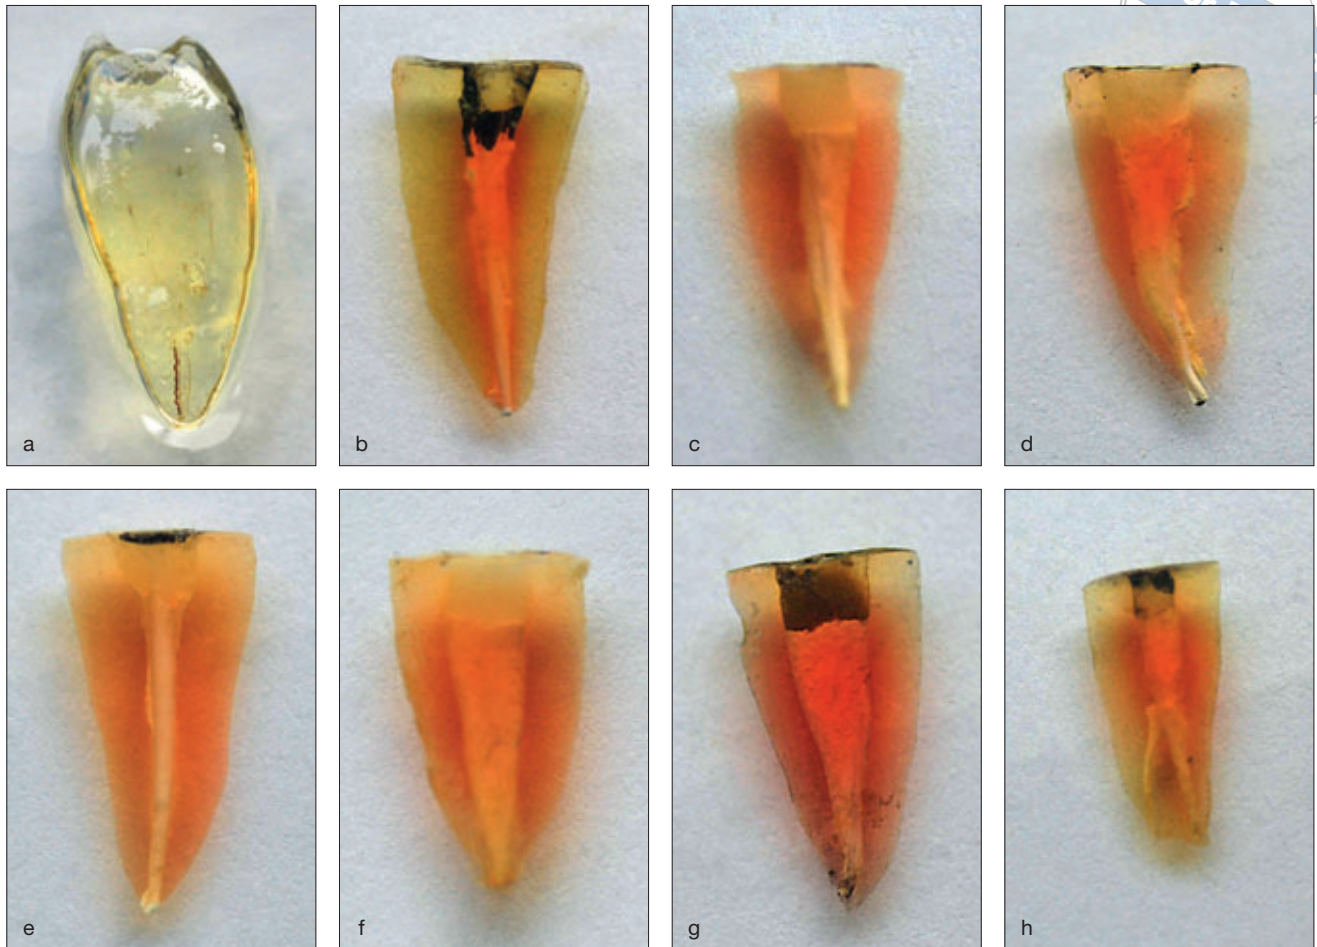


Fig 1 One representative specimen from each group: dye penetration from coronal area and throughout the root along canal walls. a: Negative group, b: Positive group, c: Esthet-X flow group, d: Beautiful flow group, e: Filtek Z350 group, f: Z100 group, g: Cavit group, h: IRM group.

Results

The mean dye penetration measurements and their standard deviations are presented in Table 2. All negative control teeth showed no dye penetration, whereas all positive control teeth demonstrated extensive dye pene-

tration. The specimens from the three flowable composite groups all showed the leakage at less than 3 mm, while the specimens from the other three experimental groups showed the maximum leakage at more than 4 mm. However, the mean dye penetration of Z100 (0.93 mm) was much less than Cavit G (1.52 mm) and

Table 3 Statistical analysis.

| Materials | Esthet-X® flow | Beautiful® flow | Filtek™ Z350 | Z100™ | Cavit™ G | IRM® |
|-----------------|----------------|------------------|------------------|------------------|--------------------|--------------------|
| Esthet-X® flow | - | <i>P</i> < 0.679 | <i>P</i> < 0.662 | <i>P</i> < 0.657 | <i>P</i> < 0.003** | <i>P</i> < 0.003** |
| Beautiful® flow | - | - | <i>P</i> < 0.808 | <i>P</i> < 0.521 | <i>P</i> < 0.008** | <i>P</i> < 0.009** |
| Filtek™ Z350 | - | - | - | <i>P</i> < 0.457 | <i>P</i> < 0.01** | <i>P</i> < 0.01** |
| Z100™ | - | - | - | - | <i>P</i> < 0.021* | <i>P</i> < 0.02* |
| Cavit™ G | - | - | - | - | - | <i>P</i> < 0.645 |
| IRM® | - | - | - | - | - | - |

*Statistically significant difference (*P* < 0.05); **Statistically significant difference (*P* < 0.01).

IRM (2.01 mm). The dye penetration from the coronal area and throughout the root along the canal walls of only one representative specimen from each group is presented in Fig 1.

The statistical analysis results are presented in Table 3. Compared with Cavit G and IRM, the three flowable composites showed significantly less leakage ($P < 0.01$). Similarly, the hybrid composite Z100 had significantly less leakage than Cavit G and IRM ($P < 0.05$). There were no statistically significant differences among the three flowable composite groups. Furthermore, no statistically significant difference in leakage was found between the three flowable composites and hybrid composite Z100, or between Cavit G and IRM.

Discussion

Application of an intra-orifice seal to prevent coronal leakage has been widely accepted¹¹. The criteria for an ideal intra-orifice seal were proposed as follows: (i) easily placed; (ii) bonds to tooth structure; (iii) seals effectively against coronal microleakage; (iv) easily distinguished from the natural tooth structure and (v) does not interfere with the final restoration of the access preparation^{6,11}.

Of the criteria, sealing against coronal microleakage and bonding to tooth structure are the most important. The present results demonstrated that flowable composites sealed as well as hybrid composite Z100 and confirmed the previous findings showing that flowable composites provided as good a seal as hybrid composites to prevent microleakage¹². The authors also demonstrated that the specimens in the Z100 group, but not the three flowable composite groups, had dye penetration into gutta-percha. This suggests that flowable composites have better adaptation to the cavity walls than the hybrid composites. Composites' adaptation to cavity walls depends on the 'resin tag'. Cavit G relies on mechanical retention and its expansion property in contact with moisture, whereas IRM only depends on mechanical retention. Moreover, flowable composites have the ability to form a layered structure of minimum thickness to improve or eliminate air inclusion or entrapment⁸. Consequently, our results showed that flowable composites and hybrid composite Z100 had significantly less leakage compared with Cavit G and IRM, which is consistent with the findings of Jenkins et al⁹. However, Sauaia et al¹⁰ had an observation opposite to the authors' results. They found that Flow-it demonstrated more leakage than Cavit G. This discrepancy might be due to the different sealers used. While Sauaia et al¹⁰ used eugenol-containing sealant, Jenkins et al⁹ and the present study used resin formulation sealer. Released eugenol

can penetrate dentine, change tooth structure and reduce shear bond strengths of composite¹³⁻¹⁵. In addition, the present results indicated that there was no significant leakage difference between Cavit G and IRM, which was difficult to compare with previous studies, since previous findings are conflicting^{5,16-20}.

Another very important criterion is that an ideal intra-orifice seal does not interfere with the final restoration of the access preparation¹¹. Most patients prefer tooth-coloured composite restorations. Thus, the material beneath composites should have no negative influence on composites. Flowable composites have been recommended as liners beneath composites due to their low viscosity, increased elasticity, and wettability, which helps relieve stresses during polymerisation shrinkage of the restorative resin²¹⁻²⁴. However, IRM is not recommended for use as a base under resin restoratives because eugenol may interfere with the polymerisation of composites²⁵.

Easy application is also an important consideration since the coronal 3 mm of the canal is a very small cavity and the materials need to be placed within canals. Adding to the advantages of high flowability, the excellent ability to penetrate into irregular spaces allows flowable resin composites to be used in situations where access is restricted or good penetration is required^{8,26}. The flowable resin composites are ideal for these situations because they are easily syringed into the cavities.

The flowable composites also meet the other criteria stated above. They can be easily distinguished from the natural tooth structure by choosing a shade in contrast to dentine. Another possible solution is to add pigment into flowable composites if necessary⁶.

In conclusion, the present study found that the flowable composites Esthet-X flow, Beautifil flow, and Filtek Z350 sealed the intra-orifice of root canals as well as hybrid composite Z100 and better than Cavit G and IRM. The results suggest that flowable composites can serve as ideal intra-orifice seals. Further *in vivo* studies and long-term evaluation are warranted.

References

1. Sriharan A. Discuss that the coronal seal is more important than the apical seal for endodontic success. *Aust Endod J* 2002;28:112-115.
2. Roghanizad N, Jones JJ. Evaluation of coronal microleakage after endodontic treatment. *J Endod* 1996;22:471-473.
3. Pisano DM, DiFiore PM, McClanahan SB, Lautenschlager EP, Duncan JL. Intraorifice sealing of gutta-percha obturated root canals to prevent coronal microleakage. *J Endod* 1998;24:659-662.
4. Balto H, Al-Nazhan S, Al-Mansour K, Al-Otaibi M, Siddiqu Y. Microbial leakage of Cavit, IRM, and Temp Bond in post-prepared root canals using two methods of gutta-percha removal: an *in vitro* study. *J Contemp Dent Pract* 2005;6:53-61.

5. Koagel SO, Mines P, Apicella M, Sweet M. *In vitro* study to compare the coronal microleakage of Tempit UltraF, Tempit, IRM, and Cavit by using the fluid transport model. *J Endod* 2008;34:442-444.
6. Wolcott JF, Hicks ML, Himel VT. Evaluation of pigmented intraorifice barriers in endodontically treated teeth. *J Endod* 1999;25:589-592.
7. Beckham BM, Anderson RW, Morris CF. An evaluation of three materials as barriers to coronal microleakage in endodontically treated teeth. *J Endod* 1993;19:388-391.
8. Hervás-García A, Martínez-Lozano MA, Cabanes-Vila J, Barjau-Escribano A, Fos-Galve P. Composite resins. A review of the materials and clinical indications. *Med Oral Patol Oral Cir Bucal* 2006;11: E215-220.
9. Jenkins S, Kulild J, Williams K, Lyons W, Lee C. Sealing ability of three materials in the orifice of root canal systems obturated with gutta-percha. *J Endod* 2006;32:225-227.
10. Sauer TS, Gomes BP, Pinheiro ET, Zaia AA, Ferraz CC. Microleakage evaluation of intraorifice sealing materials in endodontically treated teeth. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2006;102:242-246.
11. Wolcott S, Barr J. Temporary restorations in endodontics: a review. *Compend Contin Educ Dent* 2006;27:596, 599-600.
12. Yazici AR, Baseren M, Dayangac B. The effect of flowable resin composite on microleakage in class V cavities. *Oper Dent* 2003;28:42-46.
13. Hansen EK, Asmussen E. Influence of temporary filling materials on effect of dentin-bonding agents. *Scand J Dent Res* 1987;95:516-520.
14. Xie J, Powers JM, McGuckin RS. *In vitro* bond strength of two adhesives to enamel and dentin under normal and contaminated conditions. *Dent Mater* 1993;9:295-299.
15. Terata R, Nakashima K, Obara M, Kubota M. Characterization of enamel and dentin surfaces after removal of temporary cement – effect of temporary cement on tensile bond strength of resin luting cement. *Dent Mater J* 1994;13:148-154.
16. Deveaux E, Hildebert P, Neut C, Boniface B, Romond C. Bacterial microleakage of Cavit, IRM, and TERM. *Oral Surg Oral Med Oral Pathol* 1992;74:634-643.
17. Zmener O, Banegas G, Pameijer CH. Coronal microleakage of three temporary restorative materials: an *in vitro* study. *J Endod* 2004;30: 582-584.
18. Imura N, Otani SM, Campos MJ, Jardim Junior EG, Zuolo ML. Bacterial penetration through temporary restorative materials in root-canal-treated teeth *in vitro*. *Int Endod J* 1997;30:381-385.
19. Blaney TD, Peters DD, Setterstrom J, Bernier WE. Marginal sealing quality of IRM and Cavit as assessed by microbial penetration. *J Endod* 1981;7:453-457.
20. Kazemi RB, Safavi KE, Spangberg LS. Assessment of marginal stability and permeability of an interim restorative endodontic material. *Oral Surg Oral Med Oral Pathol* 1994;78:788-796.
21. Kemp-Scholte CM, Davidson CL. Complete marginal seal of Class V resin composite restorations effected by increased flexibility. *J Dent Res* 1990;69:1240-1243.
22. Beun S, Bailly C, Dabin A, Vreven J, Devaux J, Leloup G. Rheological properties of experimental Bis-GMA/TEGDMA flowable resin composites with various macrofiller/microfiller ratio. *Dent Mater* 2009;25:198-205.
23. Yazici AR, Celik C, Ozgünlaltay G. Microleakage of different resin composite types. *Quintessence Int* 2004;35:790-794.
24. Cara RR, Fleming GJ, Palin WM, Walmsley AD, Burke FJ. Cuspal deflection and microleakage in premolar teeth restored with resin-based composites with and without an intermediary flowable layer. *J Dent* 2007;35:482-489.
25. Taira J, Ikemoto T, Yoneya T, Hagi A, Murakami A, Makino K. Essential oil phenyl propanoids. Useful as OH scavengers? *Free Radic Res Commun* 1992;16:197-204.
26. Bayne SC, Thompson JY, Swift EJ, Jr., Stamatides P, Wilkerson M. A characterization of first-generation flowable composites. *J Am Dent Assoc* 1998;129:567-577.